

Microwave-Assisted Hydrothermal Synthesis of Hydroxyapatite Flakes as Substrates for Titanium Dioxide Film Deposition

Néstor Méndez-Lozano , Eduardo E. Pérez-Ramírez and Miguel de la Luz-Asunción

Campus Querétaro, Universidad del Valle de México, Blvd. Juriquilla No. 1000 A Del., Santa Rosa Jáuregui, Santiago de Querétaro C.P. 76230, Querétaro, Mexico; eduardo_perezr@my.uvm.edu.mx (E.E.P.-R.); miguel_delaluz@my.uvm.edu.mx (M.d.l.L.-A.)

* Correspondence: nestor.mendez@uvmnet.edu

Abstract: This article describes the synthesis of hydroxyapatite (HAp) flakes through a microwave-assisted hydrothermal method. These flakes suggest possible applications as a substrate for depositing titanium dioxide (TiO₂) films using chemical vapor deposition with metal–organic precursors (MOCVD). The results reveal the formation of crystalline hydroxyapatite characterized by a uniform morphology. Additionally, we demonstrated the successful deposition of TiO₂ coatings on the hydroxyapatite flakes, resulting in a distinctive faceted prism morphology. Our findings affirm the effective synthesis of the HAp/TiO₂ composite material. To further explore the material’s practical applications, we recommend assessing the photocatalytic activity of these composite membranes in future research.

Keywords: hydroxyapatite; titanium dioxide films; hydroxyapatite flakes; substrate deposition; morphological characterization



Citation: Méndez-Lozano, N.; Pérez-Ramírez, E.E.; de la Luz-Asunción, M. Microwave-Assisted Hydrothermal Synthesis of Hydroxyapatite Flakes as Substrates for Titanium Dioxide Film Deposition. *Ceramics* **2024**, *7*, 735–742. <https://doi.org/10.3390/ceramics7020048>

Academic Editor: Thierry Cabioch

Received: 5 March 2024

Revised: 30 April 2024

Accepted: 16 May 2024

Published: 28 May 2024



Copyright: © 2024 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

In recent years, the global escalating environmental challenges have intensified the exploration of using TiO₂ photocatalysts as a promising solution. These materials have predominantly found application in the remediation of pollutants in both water and air due to their versatility [1]. While powdered catalysts have demonstrated efficacy, they are not without limitations, particularly concerning challenges in stirring and subsequent separation processes [2]. In contrast, thin-film catalysts have emerged as a viable alternative, overcoming these drawbacks with multiple potential applications.

Various studies have investigated the preparation of thin TiO₂ coatings utilizing diverse synthesis techniques such as spray-coating, sol–gel, and chemical vapor deposition (CVD) [3–5]. The inherent advantage of thin TiO₂ coatings lies in their seamless integration onto substrates with irregular shapes and expansive surface areas. Recent studies have underscored the pivotal role played by morphology and crystalline structure in influencing the photocatalytic activity of these coatings [6,7].

Despite the substantial progress in this field, there remains a noteworthy gap in the literature regarding the utilization of hydroxyapatite as a substrate for TiO₂ thin films. While studies have explored various substrates such as quartz, glass, silicon, and aluminum [8], the potential of hydroxyapatite has not been extensively investigated. Previous research examined hydroxyapatite as a photocatalyst in the aqueous phase [9], albeit limited by its high band-gap energy, restricting its use to UV irradiation.

In a noteworthy departure from conventional studies, recent investigations have demonstrated the exceptional photocatalytic oxidation activity of hydroxyapatite–titanium (HAp/TiO₂) composite materials [10]. The innovation lies in harnessing the remarkable co-absorbent properties of hydroxyapatite, resulting in a substantial enhancement in photocatalytic activity. Furthermore, the environmentally friendly nature of hydroxyapatite as a calcium compound adds an extra dimension to its appeal. HAp/TiO₂ composites

offer unique advantages for TiO_2 coatings, particularly in biomedical and photocatalytic applications where enhanced biocompatibility and performance are desired. While they may involve higher initial costs and more complex fabrication processes than pure titanium substrates, the benefits they provide justify their use in specific applications where their properties are advantageous.

In the current study, we present a novel approach synthesizing TiO_2 thin films on hydroxyapatite (HAp) substrates. Our methodology involves microwave-assisted synthesis to produce hydroxyapatite flakes and chemical vapor deposition using metal–organic precursors to achieve the desired coatings. This multifaceted synthesis strategy aims to capitalize on the unique properties of hydroxyapatite and TiO_2 , offering a potential breakthrough in the development of advanced photocatalytic materials with enhanced efficiency and environmental sustainability. The goal of this study is to comprehensively analyze the morphological and structural properties of this hydroxyapatite–titanium (HAp/ TiO_2) composite material. Specifically, we aim to investigate crystalline hydroxyapatite flakes as an efficient substrate for titanium dioxide coatings. Furthermore, we suggest innovative uses for the HAp/ TiO_2 composite material, thereby contributing to the development of future research in this field.

2. Materials and Methods

Materials: Calcium nitrate [$\text{Ca}(\text{NO}_3)_2$], glutamic acid [$\text{C}_5\text{H}_9\text{NO}_4$], potassium phosphate [K_2HPO_4], and potassium hydroxide [KOH]. Distilled water was used in all synthesis steps.

Calcium nitrate [$\text{Ca}(\text{NO}_3)_2$] (1.16 g) and glutamic acid [$\text{C}_5\text{H}_9\text{NO}_4$] (4.35 g) were mixed in 300 mL of distilled water, to which glutamic acid was slowly added. The solution was stirred for 55 min at 70 °C. Meanwhile, potassium phosphate [K_2HPO_4] (1.12 g) and potassium hydroxide [KOH] (0.76 g) were mixed in 100 mL of distilled water. The solution was stirred for 15 min at 85 °C. Then, both solutions were mixed dropwise and stirred for 20 min at 85 °C. Finally, 20 glasses with 20 mL of solution were placed in the microwave oven (Monowave). The microwave conditions were a 200 °C temperature, a 10 min heating ramp, a 45 min reaction time, and a 55 min cooling time [11].

Once the process in the microwave oven was completed, the solid phase was filtered and washed with deionized water. The samples were placed in a desiccator at room temperature to obtain the hydroxyapatite flakes (HAp). The next step was to deposit the TiO_2 thin films on the HAp flakes using the metal–organic chemical vapor deposition technique (MOCVD) [12]. For this, 10 mL of acetone mixed with 20 mL of titanium isopropoxide was used as a precursor. The synthesis parameters are shown in Table 1, and the schematic diagram of the synthesis process is shown in Figure 1. After deposition, the flakes were removed from the sample holder and placed in Petri dishes. They were not subjected to any annealing process.

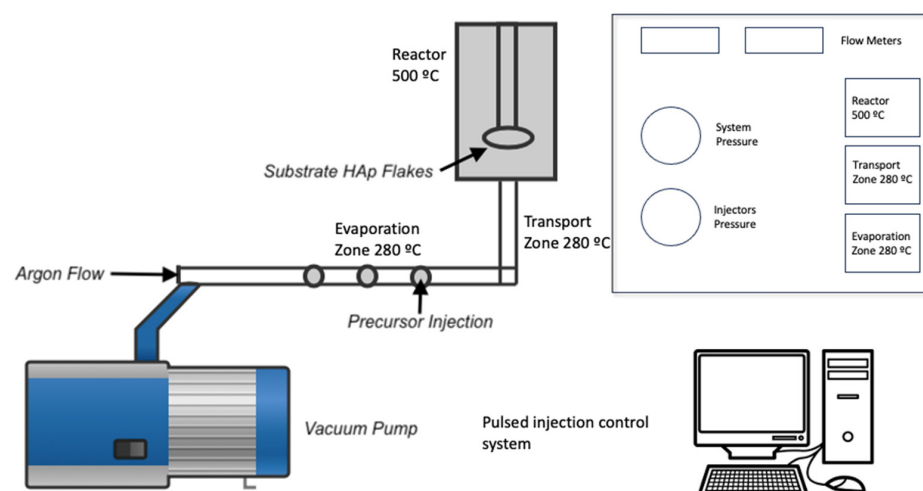


Figure 1. Schematic diagram to obtain TiO_2 coatings on hydroxyapatite flakes.

Table 1. TiO₂ deposition conditions using pulsed injection.

Substrate Temperature (°C)	Injectors Pressure (psi)	Argon Flow (L/min)	Injection Frequency (ms)
500	4.5	0.11	250

2.1. Phase Composition: X-ray Diffraction (XRD)

X-ray powder diffraction was used to identify the crystalline phases contained in all the samples. Wide-angle X-ray experiments were carried out using a Rigaku Mini Flex diffractometer and Cu k_{α} radiation ($\lambda = 1.5406 \text{ \AA}$), an accelerating voltage of 40 kV, and a current of 30 mA. Diffractograms were recorded with a Solid-State D/teX-ULTRA Detector (Rigaku, Tokyo, Japan) from 5 to 80° on a 2 θ scale and a rate of 10°/min. The spectrum analysis software MDI Jade V 5.0.37 was used [11].

2.2. Morphology and Microstructure: Scanning Electron Microscopy (SEM)

Morphological, topological, and microstructural analyses of all the samples were carried out using a JEOL JXA-8530F Scanning Electron Microscope (JEOL, Tokyo, Japan). The analysis was performed using a 2, 5, and 10 kV electron acceleration voltage, and the secondary electrons formed the images. All the samples were placed on a stainless-steel plate with a separation of 5 mm, pasted with silver paint, and covered with a gold thin film through sputtering to avoid the electrostatic charge accumulation [11].

2.3. Elemental Composition: Dispersive-Energy Spectroscopy (EDS)

To obtain the elemental composition of HAp/TiO₂ coatings, an Electronic Microprobe for Microanalysis (EPMA) JXA-8530F (JEOL, Tokyo, Japan) was used. The operation conditions were a voltage of 10 kV and a current of 0.10 nA. A small tablet was made from each sample, and then each tablet was coated with a graphite thin film [11].

3. Results and Discussion

We present diffractograms and micrographs of both sides of the flakes (Figure 2). XRD (X-ray diffraction) studies show the crystal structure corresponding to hydroxyapatite according to the Powder Diffraction File (PDF) # 01-084-1998 (Figure 2a). However, other phases of calcium phosphate are present due to the synthesis process. On the other hand, the hump present in the diffraction pattern is due to the organic residues present in the sample. The observed Bragg reflections indicate a preferential direction of growth in the (100) plane due to the use of glutamic acid during the synthesis process [11]. On the other hand (Figure 2b), the diffraction pattern corresponding to the TiO₂ coating is shown, where the indexed reflections correspond to the anatase phase of TiO₂ and the pattern shows low-intensity and well-defined peaks; however, background noise is observed. Additionally, SEM (scanning electron microscopy) micrographs of uncoated HAp flakes (Figure 2c) and TiO₂-coated HAp flakes are shown (Figure 2d). The HAp side shows a morphology of agglomerated plaques. This morphology is characteristic of the hydroxyapatite plaques reported in previous studies [13]. The TiO₂ coating (Figure 2d) shows a uniform film free of cracks, where the formation of nanostructures with well-defined faces is observed, indicating step-by-step growth. This growth occurs due to the MOCVD synthesis process using a metal–organic precursor [14].

The flakes show a compact structure; however, they can easily be divided into hydroxyapatite rods. As is well-established, the crystalline structure of hydroxyapatite is formed through the assembly of Ca type I (trigonal prisms), Ca type II (pentagonal dipyramids), phosphate groups (tetrahedra), and OH groups. The interaction mechanism of glutamic acid with this structure enables the incorporation with type I calcium, thereby inhibiting growth in the c-direction of the structure. This inhibition promotes growth in the a and b directions, consequently resulting in a plate-like morphology.

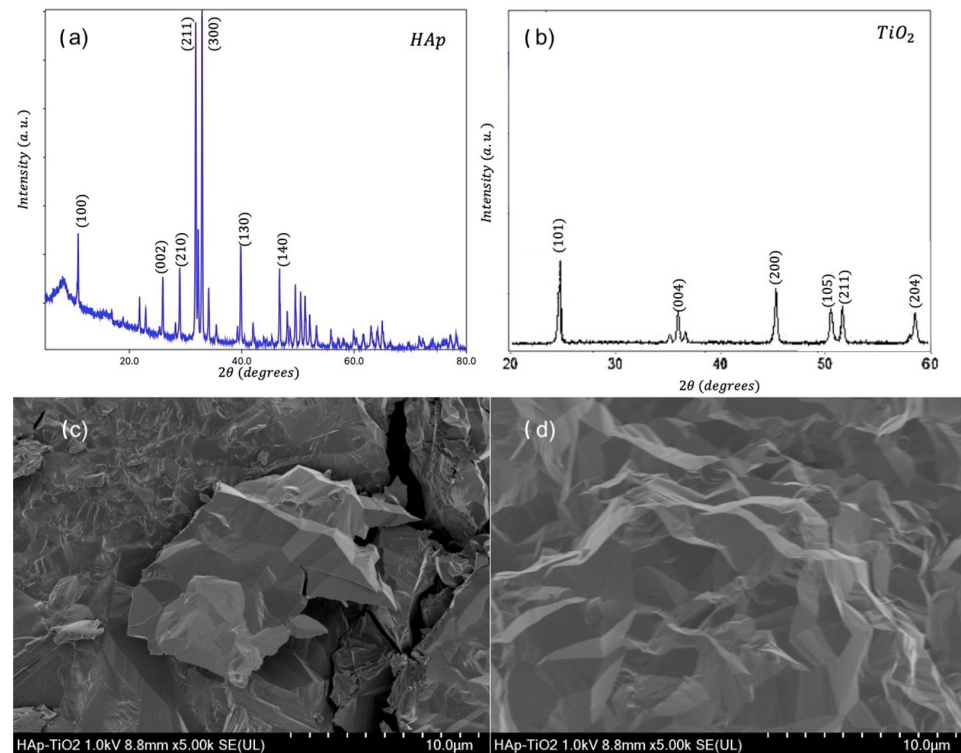


Figure 2. (a) XRD diffraction pattern of HAp flake; (b) XRD diffraction pattern of TiO₂-coated flake; (c) SEM micrograph of HAp; (d) SEM micrograph of TiO₂.

Micrographs of the hydroxyapatite flakes and TiO₂ thin films are shown (Figure 3). The hydroxyapatite flakes show a homogeneous morphology with some reliefs at magnifications of 5000× (Figure 3a); in addition, agglomerated plates with dimensions of 10 μm can be observed (Figure 3b) at 2000×.

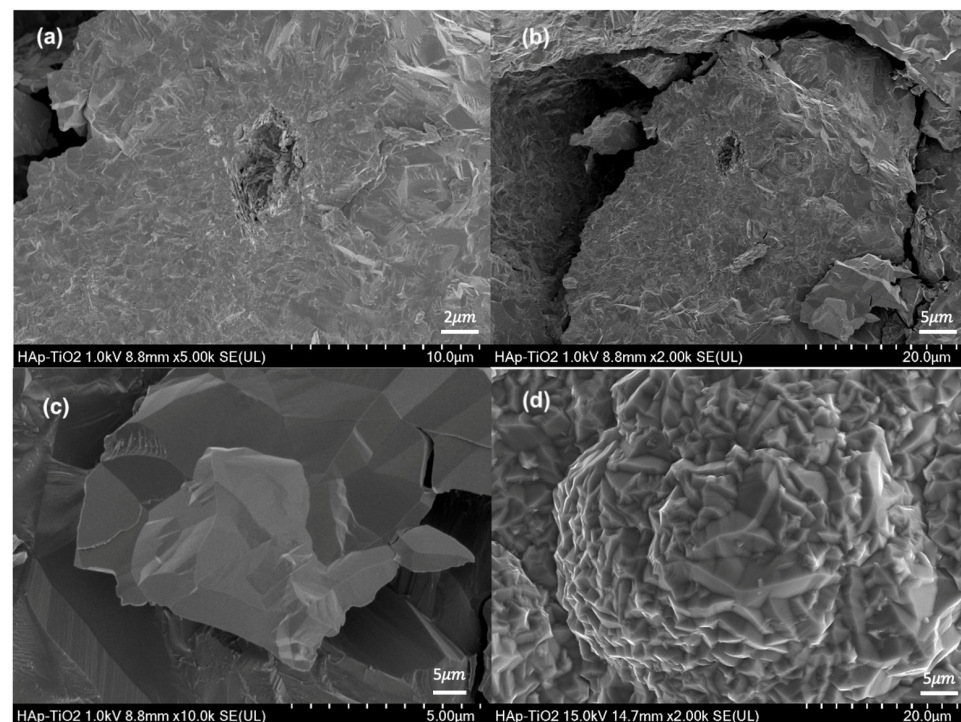


Figure 3. (a) SEM micrograph of HAp flakes at 5000×; (b) SEM micrograph of HAp flakes at 2000×; (c) SEM micrograph of TiO₂ at 5000×; (d) SEM micrograph at TiO₂ to 2000×.

Likewise, the observed plates are composed of agglomerated rods. This morphology is characteristic of the hydroxyapatite obtained through hydrothermal methods [15,16]. Hydroxyapatite flakes are obtained depending on the amount of glutamic acid used in the synthesis process and the filtration of the sample when it is removed from the microwave oven. Micrographs of the TiO₂ thin film at 5000× magnification (Figure 3c) and 2000× magnification (Figure 3d) are also shown. Both micrographs show the typical morphology of TiO₂ films obtained through MOCVD [17]. The MOCVD process allows a coating on the upper face of the hydroxyapatite flake, and a structure of densely packed crystals with a faceted prism appearance are observed. At the lowest magnification, the crystals can be observed forming a flower-like morphology. This might be due to the rearrangement of the deposited crystals. After the initial deposition of the crystals, the rearrangement process begins with their nucleation. This involves the formation of small groups of crystals from the initial material, causing flower-like growth.

EDS (energy-dispersive spectroscopy) elemental composition analyses were performed on the TiO₂ thin films (Figure 4). The results shown at 500× (Figure 4a) and 5000× (Figure 4b) magnifications reveal that the peaks predominantly correspond to Ti (titanium) and O (oxygen) and that the presence of aluminum in the spectra is due to the sample holder used during the analysis. High, sharp peaks indicate that the thin films are of high purity and were successfully deposited on the substrate. The presence of Ca and P is not visible in the spectra because only the TiO₂-coated part was analyzed. The atomic percentage of Ti in the sample was 30.89% on average. The EDS results agree with the previous DRX and SEM studies, demonstrating that the elemental composition of the thin films allowed us to determine the chemical composition of the samples. Numerous studies have considered this method for composition analysis [18]. In the EDS study, the accelerating voltage of the electron beam had a significant influence on the obtained results [19]. In Figure 5, the EDS spectrum for the hydroxyapatite flakes is depicted, revealing the presence of calcium and phosphorus with a Ca/P ratio of 1.69. Additionally, both spectra exhibit a trace amount of aluminum, measured at 0.56 wt.%.

Tables 2 and 3 show the element content in atomic percentage for TiO₂ coating and HAp flakes, respectively.

Table 2. Elemental composition of TiO₂ coating.

Element	TiO ₂ Coating	wt%
Carbon	*	0.63
Oxygen	*	41.96
Aluminum	*	0.48
Titanium	*	56.91
Calcium		0
Phosphorous		0

The asterisks represent the elements that are present in the HAp flake and the TiO₂ coating.

Table 3. Elemental composition of HAp flakes.

Element	HAp Flakes	wt%
Carbon	*	0.62
Oxygen	*	2.32
Aluminum		0.44
Titanium	*	0
Calcium	*	60.40
Phosphorous	*	36.15

The asterisks represent the elements that are present in the HAp flake and the TiO₂ coating.

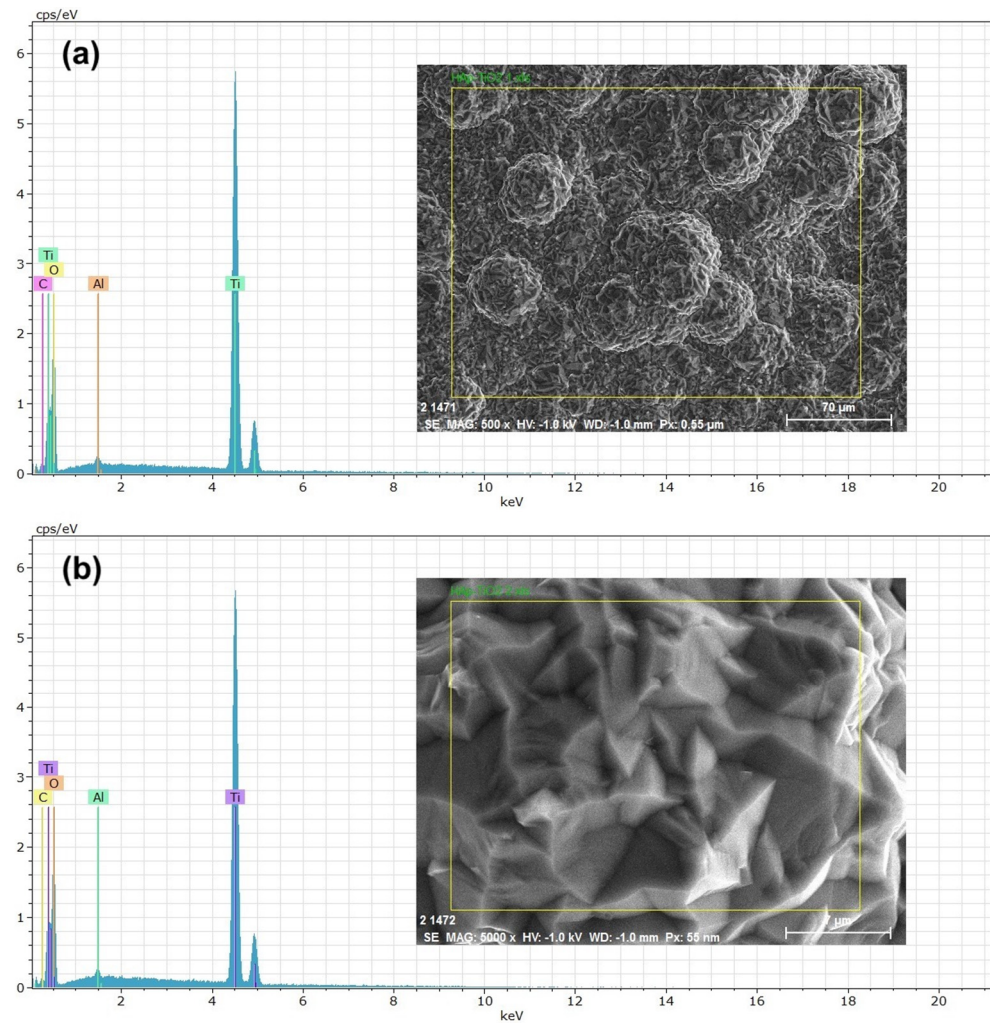


Figure 4. EDS spectra of TiO_2 coating: (a) micrograph at $\times 500$; (b) micrograph at $\times 5000$.

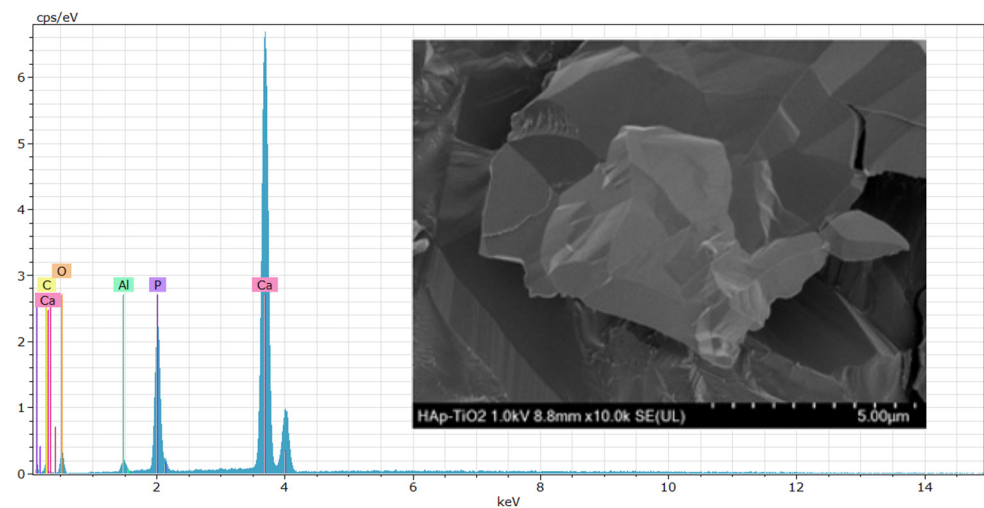


Figure 5. EDS spectra of HAp flakes.

4. Conclusions

We achieved the successful synthesis of hydroxyapatite flakes through the utilization of the microwave-assisted hydrothermal method. Notably, our investigation brought to light the significant impact of glutamic acid on the morphology of hydroxyapatite flakes, providing valuable insights into their structure. Furthermore, we extended our study to

include the synthesis of titanium dioxide (TiO₂) thin films utilizing hydroxyapatite flakes as a substrate. The X-ray diffraction (XRD) analysis revealed distinct diffraction peaks corresponding to the presence of hydroxyapatite on one side of the flake and TiO₂ in the anatase phase on the opposite side. This dual-phase formation is remarkable, showcasing the versatility of the hydroxyapatite substrate. Scanning electron microscopy (SEM) studies offer a detailed glimpse into the morphology of TiO₂ thin films, showcasing a homogeneous arrangement of faceted crystals with a prismatic appearance. The uniformity observed in this morphology enhances the potential applications of TiO₂ coating. Elemental analysis through energy-dispersive X-ray spectroscopy (EDS) has further supported our findings, elucidating the elemental composition of the coatings. This underscores the successful integration of TiO₂ coating on hydroxyapatite flakes. Our study lays the groundwork for future investigations, suggesting that we should continue exploring the photocatalytic properties of the composite material obtained (HAp/TiO₂). Additionally, these compounds have a potential application in biomedicine as a biocompatible material in tissue regeneration.

The versatile coating technique employed, metal–organic chemical vapor deposition (MOCVD), emerges as a powerful tool, providing control over the thickness and structure of TiO₂ thin films.

Author Contributions: Conceptualization N.M.-L.; methodology N.M.-L.; software, investigation, N.M.-L.; writing—original draft preparation, N.M.-L.; writing—review and editing, E.E.P.-R.; supervision, M.d.l.L.-A.; project administration, E.E.P.-R. All authors have read and agreed to the published version of the manuscript.

Funding: This research received no external funding.

Data Availability Statement: Data available on request from the authors.

Conflicts of Interest: The authors declare no conflicts of interest.

References

1. Yu, J.; Zhao, X. Effect of substrates on the photocatalytic activity of nanometer TiO₂ thin films. *Mater. Res. Bull.* **2000**, *35*, 1293–1301. [\[CrossRef\]](#)
2. Franz, S.; Falletta, E.; Arab, H.; Murgolo, S.; Bestetti, M.; Mascolo, G. Degradation of carbamazepine by photo (electro) catalysis on nanostructured TiO₂ meshes: Transformation products and reaction pathways. *Catalysts* **2020**, *10*, 169. [\[CrossRef\]](#)
3. Han, Z.; Chang, V.W.; Zhang, L.; Tse, M.S.; Tan, O.K.; Hildemann, L.M. Preparation of TiO₂-coated polyester fiber filter by spray-coating and its photocatalytic degradation of gaseous formaldehyde. *Aerosol Air Qual. Res.* **2012**, *12*, 1327–1335. [\[CrossRef\]](#)
4. Cotalan, N.; Rak, M.; Bele, M.; Cör, A.; Muresan, L.M.; Milošev, I. Sol-gel synthesis, characterization, and properties of TiO₂ and Ag-TiO₂ coatings on titanium substrate. *Surf. Coat. Technol.* **2016**, *307*, 790–799. [\[CrossRef\]](#)
5. Lee, H.; Song, M.Y.; Jurng, J.; Park, Y.K. The synthesis and coating process of TiO₂ nanoparticles using CVD process. *Powder Technol.* **2011**, *214*, 64–68. [\[CrossRef\]](#)
6. Komaraiah, D.; Radha, E.; Sivakumar, J.; Reddy, M.R.; Sayanna, R. Photoluminescence and photocatalytic activity of spin coated Ag+ doped anatase TiO₂ thin films. *Opt. Mater.* **2020**, *108*, 110401. [\[CrossRef\]](#)
7. Dundar, I.; Krichevskaya, M.; Katerski, A.; Acik, I.O. TiO₂ thin films by ultrasonic spray pyrolysis as photocatalytic material for air purification. *R. Soc. Open Sci.* **2019**, *6*, 181578. [\[CrossRef\]](#) [\[PubMed\]](#)
8. Latif, N.T.; Rzaiz, J.M. Concentration Effect of Mixed SnO₂-ZnO on TiO₂ Optical Properties Thin Films prepared by Chemical Spray Pyrolysis Technique. *J. Univ. Anbar Pure Sci.* **2020**, *14*, 43–49. [\[CrossRef\]](#)
9. Sheng, G.; Qiao, L.; Mou, Y. Preparation of TiO₂/hydroxyapatite composite and its photocatalytic degradation of methyl orange. *J. Environ. Eng.* **2011**, *137*, 611–616. [\[CrossRef\]](#)
10. Sánchez-Hernández, A.K.; Martínez-Juárez, J.; Gervacio-Arciniega, J.J.; Silva-González, R.; Robles-Águila, M.J. Effect of ultrasound irradiation on the synthesis of hydroxyapatite/titanium oxide nanocomposites. *Crystals* **2020**, *10*, 959. [\[CrossRef\]](#)
11. Méndez-Lozano, N.; Velázquez-Castillo, R.; Rivera-Muñoz, E.M.; Bucio-Galindo, L.; Mondragón-Galicia, G.; Manzano-Ramírez, A.; Apátiga-Castro, L.M. Crystal growth and structural analysis of hydroxyapatite nanofibers synthesized by the hydrothermal microwave-assisted method. *Ceram. Int.* **2017**, *43*, 451–457. [\[CrossRef\]](#)
12. Apátiga, L.M.; Castano, V.M. Magnetic behavior of cobalt oxide films prepared by pulsed liquid injection chemical vapor deposition from a metal-organic precursor. *Thin Solid Films* **2006**, *496*, 576–579. [\[CrossRef\]](#)
13. Méndez-Lozano, N.; Apatiga-Castro, M.; Soto, K.M.; Manzano-Ramírez, A.; Zamora-Antunano, M.; Gonzalez-Gutierrez, C. Effect of temperature on crystallite size of hydroxyapatite powders obtained by wet precipitation process. *J. Saudi Chem. Soc.* **2022**, *26*, 101513. [\[CrossRef\]](#)

14. Apátiga, L.M.; Rubio, E.; Rivera, E.; Castaño, V.M. Surface morphology of nanostructured anatase thin films prepared by pulsed liquid injection MOCVD. *Surf. Coat. Technol.* **2006**, *201*, 4136–4138. [[CrossRef](#)]
15. Burdusel, A.C.; Neacsu, I.A.; Birca, A.C.; Chircov, C.; Grumezescu, A.M.; Holban, A.M.; Andronescu, E. Microwave-Assisted Hydrothermal Treatment of Multifunctional Substituted Hydroxyapatite with Prospective Applications in Bone Regeneration. *J. Funct. Biomater.* **2023**, *14*, 378. [[CrossRef](#)] [[PubMed](#)]
16. Nandihalli, N.; Gregory, D.H.; Mori, T. Energy-saving pathways for thermoelectric nanomaterial synthesis: Hydrothermal/solvothermal, microwave-assisted, solution-based, and powder processing. *Adv. Sci.* **2022**, *9*, 2106052. [[CrossRef](#)]
17. Galenda, A.; Natile, M.M.; El Habra, N. Large-Scale MOCVD Deposition of Nanostructured TiO₂ on Stainless Steel Woven: A Systematic Investigation of Photoactivity as a Function of Film Thickness. *Nanomaterials* **2022**, *12*, 992. [[CrossRef](#)] [[PubMed](#)]
18. Cotrut, C.M.; Vladescu, A.; Dinu, M.; Vranceanu, D.M. Influence of deposition temperature on the properties of hydroxyapatite obtained by electrochemical assisted deposition. *Ceram. Int.* **2018**, *44*, 669–677. [[CrossRef](#)]
19. Miculescu, F.; Luță, C.; Constantinescu, A.E.; Maidaniuc, A.; Mocanu, A.C.; Miculescu, M.; Voicu, S.I.; Ciocan, L.T. Considerations and influencing parameters in EDS microanalysis of biogenic hydroxyapatite. *J. Funct. Biomater.* **2020**, *11*, 82. [[CrossRef](#)] [[PubMed](#)]

Disclaimer/Publisher’s Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.