

Article

Qualitative Anatomical Characteristics and Fiber Quality of Tapped *Styrax sumatrana* Wood Grown in North Sumatra, Indonesia

Atmawi Darwis ^{1,†} , Byantara Darsan Purusatama ^{2,†} , Apri Heri Iswanto ^{3,*} , Nam-Hun Kim ^{4,*}, Rudi Hartono ³ and Arida Susilowati ⁵

¹ School of Life Sciences and Technology, Institut Teknologi Bandung, Gedung Labtex XI, Jalan Ganesha 10, Bandung 40132, Indonesia; atmawi@itb.ac.id

² Institute of Forest Science, Kangwon National University, Chuncheon 24341, Republic of Korea; byantara@kangwon.ac.kr

³ Department of Forest Product, Faculty of Forestry, Universitas Sumatera Utara, Medan 20155, Indonesia; rudihartono@usu.ac.id

⁴ Department of Forest Biomaterials Engineering, College of Forest and Environmental Sciences, Kangwon National University, Chuncheon 24341, Republic of Korea

⁵ Department of Sylviculture, Faculty of Forestry, Universitas Sumatera Utara, Medan 20155, Indonesia

* Correspondence: apri@usu.ac.id (A.H.I.); kimnh@kangwon.ac.kr (N.-H.K.)

† These authors contributed equally to this work.

Abstract: This study investigated the qualitative anatomical characteristics and fiber quality of tapped *Styrax sumatrana* wood to facilitate its further utilization. The transverse surface of the tapped *S. sumatrana* was light or greyish brown in the sapwood and reddish brown in the heartwood. The resin canals of the tapped wood were formed along the growth rings at the boundaries between the heartwood and sapwood. Furthermore, microscopic analyses revealed an irregular outline and rounded epithelial cells at the edges of the intercellular traumatic canal (TC). Approximately 8–16 epithelial cells surrounded the resin canals. The fibers in the tapped *S. sumatrana* were generally thin-walled, whereas those near the TC were thick-walled. Moreover, *S. sumatrana* were diffuse-porous and exhibited intermediately distinct or indistinct growth ring boundaries. The vessels were mainly radial multiples and clusters of 3–5. In addition, they showed a diagonal-to-radial pattern arrangement and a few tangential bands. Deposits were observed in some vessels in the tapped part but were absent in the untapped part. The fiber length of the tapped *S. sumatrana* wood was classified as moderate to extensive and categorized as second-grade pulp quality. Finally, the cell walls were classified as thin to moderate.

Keywords: qualitative anatomical characteristics; tapped *Styrax sumatrana* wood; intercellular traumatic canal; fiber quality



Citation: Darwis, A.; Purusatama, B.D.; Iswanto, A.H.; Kim, N.-H.; Hartono, R.; Susilowati, A. Qualitative Anatomical Characteristics and Fiber Quality of Tapped *Styrax sumatrana* Wood Grown in North Sumatra, Indonesia. *Forests* **2024**, *15*, 509. <https://doi.org/10.3390/f15030509>

Academic Editor: Holger Gärtner

Received: 6 February 2024

Revised: 29 February 2024

Accepted: 6 March 2024

Published: 8 March 2024



Copyright: © 2024 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Plants can produce exudates that usually come out when plants are injured. The exudates cover the wound and harden after being exposed to air [1,2]. Resin, latex, and gum are the common exudates used. Resin is a type of exudate consisting of terpenoids or phenolics and is secreted by internal or surface glands of plant tissues [3,4].

One of the plant genera that produce resinous exudates is *Styrax* spp. The *Styrax* genus, which belongs to the family *Styracaceae*, comprises approximately 130 species [5]. It has major habitats in the tropical, subtropical, and temperate regions of Asia, Europe, and America [6]. Three *Styrax* species have been identified in Southeast Asia: *Styrax benzoin*, *Styrax paralleloneurum* synonymous with *Styrax sumatrana*, and *Styrax tonkinensis*.

The *Styrax* spp. is one of the most important plants in North Sumatra and has been utilized to produce a resin called benzoin. Benzoin has high economic value as a raw material for cosmetics, perfume binders, preservatives, and raw materials for pharmaceutical drugs,

a natural antioxidant resource, and flavor enhancers in the food industry [7–9]. The *Styrax* spp., apart from producing resin to be used for various uses, as mentioned, the wood also has the potential to be used for various purposes, such as light construction, furniture, and handy craft materials [9].

S. sumatrana can reach a height of 35 m and a diameter at breast height (DBH) of 40–60 cm. This wood is suitable for light construction, furniture manufacturing, handicrafts, pulp, and paper [6–9]. *S. sumatrana*, known as the kemenyan, haminjon toba, or benzoin tree, is a commercial tree endemic to North Sumatra, Indonesia. The area of *Styrax* plantation in North Sumatra was 23,172 ha, with a total resin production of 8845 tons [10].

The *S. sumatrana* resin is harvested through mechanical treatment of the stem. A few holes with a depth of 3–5 cm are made in the stems using a sharp object and patted every four days for three months. The resin is subsequently harvested 3–4 months after treatment [11]. The productive period of this tree as a resin producer is approximately 20 years, and Sumatra residents typically use it for firewood after its productive years. Following the productive phase, the resin tapping process leaves distinctive tapping scars on the wood of the *Styrax* tree.

Intercellular traumatic canals (TCs) may develop in response to various types of injuries, such as physical damage, infections, and insect attacks. Typically, these canals consist of epithelial cells producing natural resin and are organized in tangential bands or exist as a singular canal [12]. Intercellular traumatic resin canals are found in various species, such as the Meliaceae family, due to mechanical stimuli [12], *Tsuga sieboldii* by piercing metal pins around the stem [13], and *Picea engelmannii* due to the attack of *Dendroctonus rufipennis* [14]. In addition, Deng et al. [15] revealed that traumatic resin canals in *Styrax* are formed by parenchymal cells in the secondary xylem by schizolysigeny after injury.

Previous studies have demonstrated the anatomical characteristics of *Styrax* wood grown in Indonesia. Pasaribu et al. [16] reported that *S. sumatrana* generally shows distinctive anatomical characteristics with *S. paralleloneurum*. *S. sumatrana* and *S. paralleloneurum* showed multiseriate rays with three to six and three to four seriate rays, respectively. Moreover, *S. paralleloneurum* showed a large intercellular traumatic resin (TC), whereas *S. sumatrana* had a small TC in the growth ring. However, the fiber quality of both species was categorized as first-grade pulp quality.

S. sumatrana grown in North Sumatra is commonly wounded by resin tapping, which may affect its anatomical characteristics. So far, the anatomical characteristics of tapped *S. sumatrana* wood remain understudied. Therefore, the present study investigated the qualitative anatomical characteristics and fiber quality of tapped *S. sumatrana* according to the IAWA list for hardwood identification to provide valuable information on wood identification and quality to facilitate further utilization of the species.

2. Materials and Methods

2.1. Materials

The basic information of the sampled tree was derived from a previous study [9]. A 15-year-old *S. sumatrana* tree tapped by the local community for resin harvesting was used in this study. The tree was located at an altitude of approximately 900 m above sea level in Banuaji IV village in the Adiankoting sub-district, North Tapanuli regency, North Sumatra, Indonesia (2°0′10.08″ N, 99°4′14.52″ E). A wood disc with 11.5 cm in diameter and 10 cm in thickness was obtained from the diameter breast height. The air-dry specific gravity of the wood sample was 0.58.

2.2. Methods

2.2.1. Macroscopic and Microscopic Observation

The transverse surfaces of the wood disc underwent abrasion with coarse sandpaper (plate number 1 from Deerfos Co., Ltd. in Incheon, Korea) via a sanding machine (TW/BD-46 model, running at 2070 rpm and 450 W from Rexon Industrial Corp., Ltd. in Taichung, Taiwan). Following this initial sanding, the wood discs were manually sanded

with fine sandpaper (CC-600Cw from Daesung Abrasive Co., Ltd. in Seoul, Korea). The macroscopic structures of the transverse and longitudinal surfaces were observed under a stereo microscope (SMZ 745T, Nikon, Tokyo, Japan)

Here, three wood blocks with dimensions of 20 (L) $\times$ 20 (R) $\times$ 20 (T) mm³ were extracted from the tapped and untapped parts near the bark of the wood discs for microscopic observation. The optical microscopy in the present study was performed according to Savero et al. [17]. The samples were soaked in a mixture of glycerin and water (50:50) and heated on a heating plate for 30–45 min. Cross, tangential, and radial sections with approximately 20 μ m thickness were prepared using a sliding microtome (Nippon Optical Works Co., Ltd., Nagano, Japan). All slices were stained with 1% safranin and 1% light-green solution. Additionally, they were dehydrated using a graded series of alcohol (50, 70, 90, 95, and 99%) and xylene. Permanent slides were prepared using Canada balsam. The stained sections were observed using an optical microscope (Eclipse Si, Nikon, Tokyo, Japan) connected to i-Solution-lite version 26.1 software (IMT i-Solution Inc., Burnaby, BC, Canada).

For the scanning electron microscopy, 0.5 $\times$ 0.5 $\times$ 0.5 cm³ wood samples were vacuumed and coated with gold using a sputter coater (Cressington sputter coater 108; Watford, UK). The samples were observed using a scanning electron microscope (JEOL JSM-6360, 15 kV, Tokyo, Japan).

2.2.2. Cell Maceration

Matchstick-sized samples were prepared for maceration. The wood samples were macerated in a boiling solution containing 60% glacial acetic acid and 30% hydrogen peroxide at 80 °C for 1–2 h [18]. The macerated samples were rinsed under running tap water until neutralization. Next, fibers were separated using a pin while washing in distilled water. The fibers were stained using 1% safranin solution for approximately 3 h and then washed with distilled water. They were subsequently arranged on a microscope slide, dripped with glycerin, and mounted with a cover glass for observation under an optical microscope (Eclipse Si, Nikon, Tokyo, Japan) connected to i-Solution Lite software (IMT i-Solution Inc., Burnaby, BC, Canada).

2.2.3. Measuring Dimensions of Vessels and Fibers, as Well as Their Derivative Value

The fiber length and diameter, lumen diameter, and vessel length and diameter were each measured using 25 cells. The derivative values of the fiber, such as the Runkel ratio (RR), felting power (FP), mulhsteph ratio (MR), coefficient rigidity (CR), and flexibility ratio (FR), were analyzed to elucidate the quality of the wood fiber for pulp and paper production. The fiber quality was determined as previously described [19], as shown in Table 1. The pulp quality classification is shown in Table 2. Fibers were subsequently separated using a pin while washing in distilled water.

Table 1. Fiber derivative values and their formula equation.

The Derivative Values of Fiber	Equation
Runkel ratio (RR)	$\frac{2W}{ld}$
Felting power (FP)	$\frac{L}{D}$
Mulhsteph ratio (MR)	$\frac{(D^2 - ld^2)}{D^2} \times 100\%$
Coefficient rigidity (CR)	$\frac{W}{D}$
Flexibility ratio (FR)	$\frac{ld}{D}$

Table 2. Pulp quality classification [19,20].

Parameter	Class I		Class II		Class III		Class IV	
	Value	Score	Value	Score	Value	Score	Value	Score
Fiber length (μm)	2200	100	1600–2200	75	900–1600	50	900	50
Runkel ratio	0.25	100	0.25–0.5	75	0.5–1.0	50	1.0	50
Felting power	90	100	70–90	75	40–70	50	40	50
Flexibility ratio	0.8	100	0.6–0.8	75	0.4–0.6	50	0.6	50
Coefficient of rigidity	0.1	100	0.1–0.15	75	0.15–0.2	50	0.2	50
Mulhsteph ratio	30%	100	30%–60%	75	60%–80%	50	80%	50
Total score	451–600		301–450		151–300		150	

3. Results and Discussion

3.1. Macroscopic Characteristics in the Transverse and Longitudinal Surfaces

Figure 1 shows the transverse, tangential, and radial surfaces of an *S. sumatrana* wood disc wounded by tapping. *S. sumatrana* wood showed light or greyish-brown sapwood and reddish-brown heartwood on the transverse surface. The heartwood proportion was higher than that of sapwood (3:1). Pasaribu et al. [16] reported that untapped *S. sumatarana* and *S. paralleloneurum* were light brown or slightly grayish-brownish-yellow and that there was no color difference between heartwood and sapwood in either species. Similarly, Damayanti et al. [21] reported that *S. benzoin* was light brown or slightly grayish-brownish-yellow, whereas the heartwood and sapwood showed no color difference.

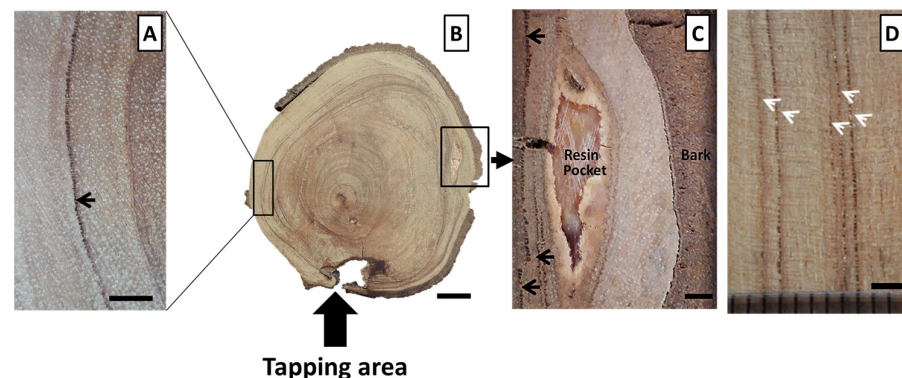


Figure 1. Transverse (A–C) and radial surfaces (D) of a tapped *Styrox sumatrana* wood disc. The resin pocket can be seen in (C). The dark lines (arrows in (A,C,D)) in the transverse and radial surfaces indicate traumatic intercellular canal bands. Scale bars: 2 mm (A,C,D) and 30 mm (B).

S. sumatrana wood showed clear TCs, forming a complete ring and a resin pocket consisting of whitish substances in the earlywood (Figure 1A,C). The radial section showed clear dark lines representing a TC in the longitudinal direction (Figure 1D). In other hardwood species, Dünisch and Baas [12] mentioned that *Meliaceae* species had two kinds of channels between cells: single or small groups of channels (called local intercellular canals), and the other type formed thin bands of channels along the outer edge of the wood disc. The length of the TC was extended from millimeters to a couple of meters and, in some cases, could be extended down the entire axis of the tree.

3.2. Microscopic Characteristics

3.2.1. Cross-Sections

Optical micrographs of cross-sections of the tapped and untapped parts of *S. sumatrana* are presented in Figure 2. The wood discs showed an intermediate between distinct and

indistinct growth ring boundaries, with diffuse-porous vessels observed (Figure 2A,B). The vessels were mainly in radial multiples and clusters of three to five and partly solitary. They also showed an angular outline (Figure 2C,D). In addition, *S. sumatrana* tended to have a diagonally to radially arranged pattern and a few tangential vessel bands. Gum or deposits were observed in some vessels in the tapped part (Figure 2B), whereas they were absent in the untapped part of the wood discs (Figure 2A). The number of vessels and diameter of vessel lumina were 7–11 per mm² and 96–190 (131 ± 28) μm , respectively.

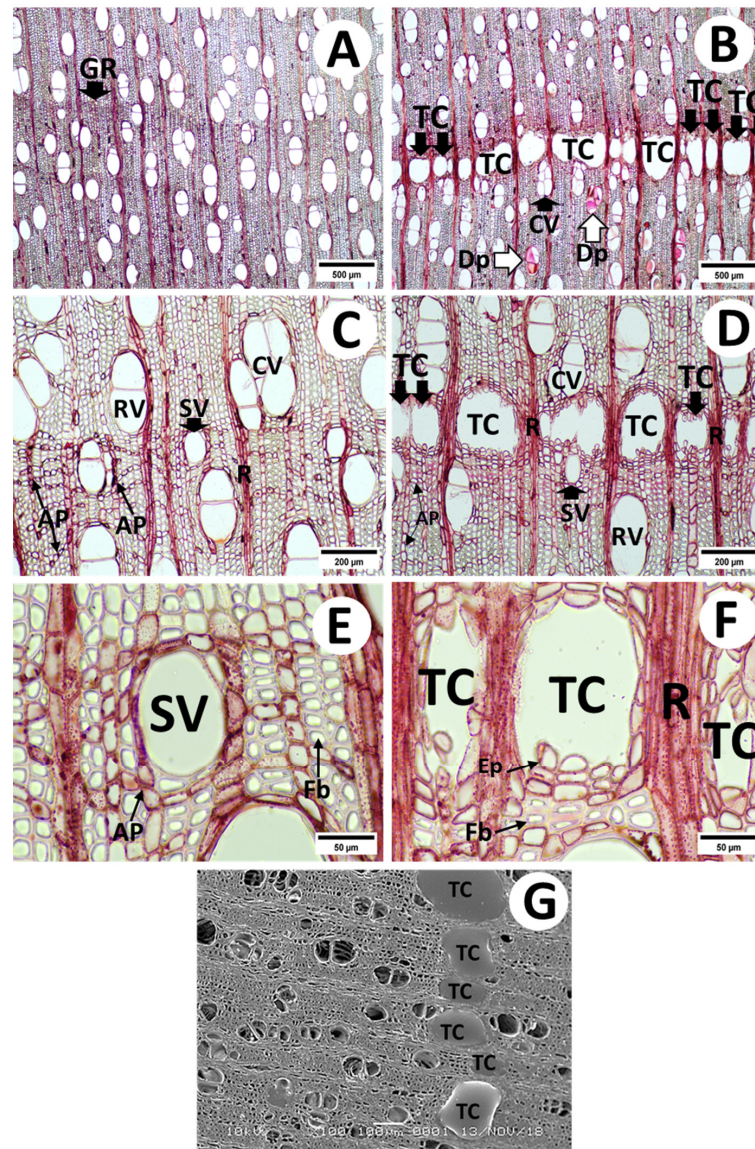


Figure 2. The optical (A–F) and scanning electron (G) micrographs of cross-sections of the untapped (A,C,E) and tapped (B,D,F,G) parts in tapped *S. sumatrana*. Growth ring (GR), traumatic resin canals (TCs), clustered vessels (CVs), radially arranged vessels (RVs), solitary vessels (SVs), deposits in vessels (Dp), rays (Rs), axial parenchyma (AP), fibers (Fb), and epithelial cells (Ep). Scale bars: 500 μm (A,B), 200 μm (C,D), 50 μm (E,F), and 100 μm (G).

TCs were arranged in tangential bands resembling growth rings (Figure 2B,D,G). In addition, the TC showed an irregular outline and rounded parenchymal cells (epithelial cells) at the edges of the canal. Approximately 8–16 epithelial cells surrounded these resin canals (Figure 2F), and TCs fulfilled with resin are also shown in Figure 2G. The fibers in the tapped and untapped parts of *S. sumatrana* were generally thin-walled, whereas those near the TC were thick-walled (Figure 2E,F). The apotracheal axial parenchyma was diffused

and diffused-in-aggregate, whereas the paratracheal axial parenchyma was vasicentric and banded, including reticulate, narrow, and marginal bands (Figure 2C–E).

Tapped *S. sumatrana* generally showed anatomical characteristics comparable to *Styrax* wood [16,21]. These studies identified mechanical treatment during resin tapping as the cause of TC in *Styrax* wood and other hardwoods. Pasaribu et al. [16] reported that TCs were formed at the growth ring boundary of untapped *S. sumatrana* and *S. paralleloneurum*. However, the TC that formed in *S. paralleloneurum* was larger than that in *S. sumatrana*. Damayanti et al. [21] and Pasaribu et al. [16] attributed these differences in TC size to genetic differences or natural wounding during wood harvesting. Dünisch and Baas [12] observed that wounded *Meliaceae* species typically developed intercellular canals, which were commonly found either individually or in small clusters, often appearing as thin tangential bands. They also mentioned that there were thick-walled fibers and increased production of reddish to dark red-colored accessory compounds near the intercellular canals. Rounded parenchyma cells were frequent at the edges of intercellular canals and may extend into the secretion.

3.2.2. Radial and Tangential Sections

Optical micrographs of the radial and tangential sections of tapped *S. sumatrana* are shown in Figures 3 and 4, respectively. Procumbent body ray and square marginal cells were observed in the radial section (Figure 3A). Epithelial cells were observed at the edges of the TC, whereas a rejuvenated ray was observed within the TC (Figure 3B). The vessels contained scalariform perforation plates (Figure 3C). The width of the rays was uniseriate to multiseriate (two to four seriates) (Figure 4A), and the fibers were non-septated and septated with distinctly bordered pits (Figure 4A,B) in the tangential section. The intervessel pits were alternating (Figure 4C), and the vessel ray pits had distinct borders in size and shape, similar to the intervessel pits (Figure 4D). Chambered prismatic oxalate crystals were observed in the axial (Figure 5A) and ray (Figure 5B) parenchyma. Silica grains were also observed in the ray cells (Figure 5C). Dickison and Phend [22] found crystals in the ray cells of *Styrax hypargyreus*, *Styrax officinalis*, and *Styrax suberifolius*. In addition, silica grains were found in *Styrax argenteus*, *Styrax fanshawei*, *Styrax glabratus*, *Styrax guianensis*, *S. hypargyreus*, *Styrax hypochryseus*, *Styrax leprosus*, *Styrax pallidus*, and *Styrax tarapotensis*. However, Pasaribu et al. [16] reported the absence of silica in *S. sumatrana*.

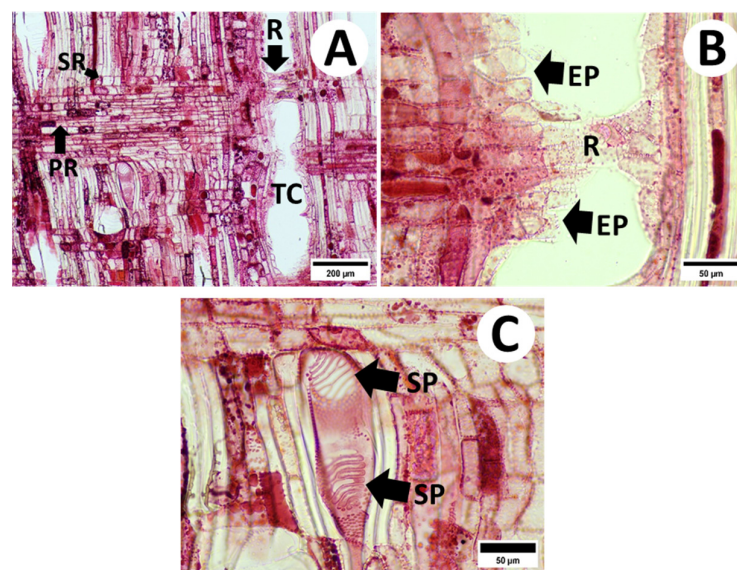


Figure 3. Optical micrographs of the radial section in tapped *S. sumatrana*. Square body ray (SR), procumbent body ray (PR), traumatic intercellular canal (TC), epithelial cells (EP), rejuvenated ray (R), and scalariform perforation plate (SP). Scale bars: 200 µm (A), 50 µm (B,C).

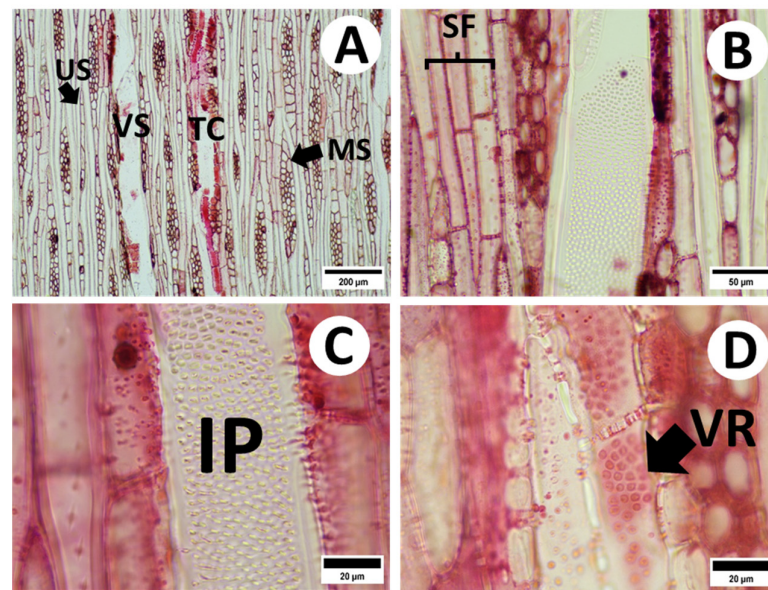


Figure 4. Optical micrographs of the tangential section in tapped *S. sumatrana*. Multiseriate (MS) and uniseriate rays (US), septate fibers with bordered pits (SFs), intervessel pits (IPs), vessel (VS) and vessel-ray pits (VR). Scale bars: 200 µm (A), 50 µm (B), and 20 µm (C,D).

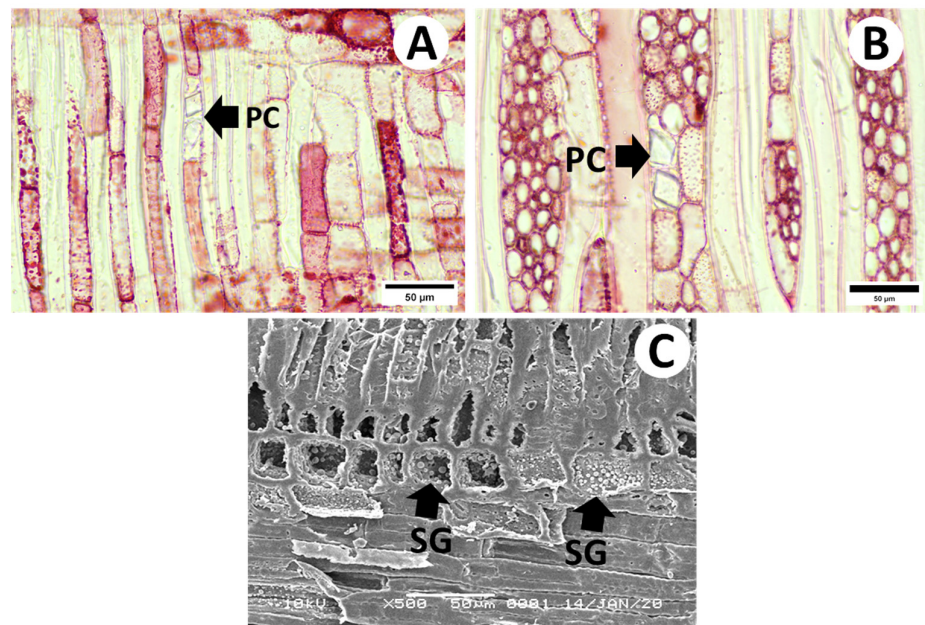


Figure 5. Oxalate prismatic crystals (PCs) in axial (A) and ray (B) parenchyma, as well as silica grain (SG) in ray parenchyma (C) of tapped *S. sumatrana* wood. Scale bars: 50 µm.

3.3. Vessel and Fiber Characteristics

Optical micrographs of the cell components of tapped *S. sumatrana* are shown in Figure 6. The vessel elements were tubes with tails at both ends (Figure 6A), with a few vessels showing parallel and opposite arrangements of the perforation plates on the tips of their elements (Figures 4, 5 and 6A).

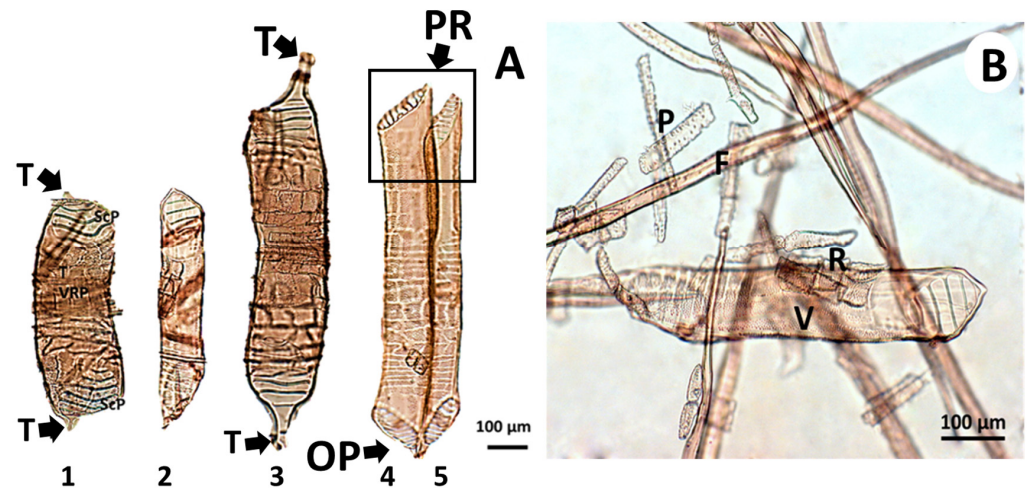


Figure 6. The compositions of cells in tapped *S. sumatrana*. (A) Vessel elements (1–5), tails of vessel element (T), parallel (PR) and opposite (OP) perforation plates between 4 and 5. (B) Fibers (F), parenchyma cell (P), vessel element (V), and ray (R). Scale bars: 100 μm .

The length of the vessels ranged from 436 to 965 μm , and the average was $721 \pm 171 \mu\text{m}$, showing feature 53 in the IAWA list for hardwood identification [23]. The vessel length of *S. sumatrana* in the present study was shorter than that of *Styrax* wood in previous studies [16,21,24]. Pasaribu et al. [16] reported a *S. sumatrana* vessel length of 396–1449 μm and an average of $1031 \pm 178 \mu\text{m}$. In addition, the vessel length of *S. paralleloneurum* was 671–1374 μm , and the average was $1026 \pm 187 \mu\text{m}$. In addition, the vessel length of *S. paralleloneurum* was 671–1374 μm , and the average was $1026 \pm 187 \mu\text{m}$. Damayanti et al. [21] reported *S. benzoin* and *S. paralleloneurum* vessel element lengths of $1135 \pm 168 \mu\text{m}$ and $1055 \pm 166 \mu\text{m}$, respectively. Machado et al. [24] reported that the vessel lengths of *Styrax latifolium*, *Styrax martii*, *Styrax leprosus*, and *Styrax camporum* from Brazil were $970 \pm 197 \mu\text{m}$, $873 \pm 197 \mu\text{m}$, $853 \pm 157 \mu\text{m}$, and $738 \pm 121 \mu\text{m}$, respectively.

The vessel lumina diameter of *S. sumatrana* ranged from 96 to 190 with an average of $131 \pm 28 \mu\text{m}$, showing feature 40 in the IAWA list for hardwood identification [23]. As reported by Pasaribu et al. [16] and Damayanti et al. [21], vessel lumina diameters of *S. sumatrana*, *S. benzoin*, and *S. paralleloneurum* were $168 \pm 37 \mu\text{m}$, $160 \pm 21 \mu\text{m}$, and $140 \pm 25 \mu\text{m}$, respectively, showing larger value than *S. sumatrana* in the present study. Machado et al. [24] reported that the vessel lumina diameters of *Styrax latifolium*, *Styrax martii*, *Styrax leprosus*, and *Styrax camporum* from Brazil were $91 \pm 14 \mu\text{m}$, $97 \pm 17 \mu\text{m}$, $69 \pm 17 \mu\text{m}$, and $72 \pm 14 \mu\text{m}$, respectively, which is distinctively smaller than the vessel lumina diameter of *S. sumatrana* in the present study.

The dimensions and derivative values of the tapped *S. sumatrana* wood fibers are listed in Table 3. The fiber length was 1390.8 μm , which is categorized into moderate to extensive based on the Hardwood List of the IAWA Committee [23]. The fiber length of *S. sumatrana* was smaller than that of *Styrax* wood reported in previous studies. Pasaribu et al. [18] reported that the fiber length and diameter of untapped *S. sumatrana* ranged from 1525 to 2290 μm , and the average was $1860 \pm 163 \mu\text{m}$. Damayanti et al. [21] reported an *S. benzoin* fiber length of $1930 \pm 184 \mu\text{m}$ and an *S. paralleloneurum* fiber length of $1870 \pm 139 \mu\text{m}$. Machado et al. [24] reported that the fiber lengths of *Styrax latifolium*, *Styrax martii*, and *Styrax leprosus* were $1904 \pm 317 \mu\text{m}$, $1798 \pm 262 \mu\text{m}$, and $1811 \pm 294 \mu\text{m}$, respectively.

The fiber diameter was 29.23 μm , whereas the wall thickness and fiber lumina diameter were 5.62 μm and 17.99 μm , respectively. The fiber wall of *S. sumatrana* in the present study was classified as thin to moderate based on the Hardwood List of the IAWA Committee [23]. Damayanti et al. [21] mentioned that the fiber wall thickness and lumen diameter of tapped *S. benzoin* were 2.3 ± 0.4 and 32.5 ± 3.1 , respectively. The fiber walls of untapped *S. sumatrana* and tapped *S. benzoin* in previous studies were distinctively thinner than those of tapped *S. sumatrana* in the present study. Pasaribu et al. [16] reported that the fiber

and lumina diameter of untapped *S. sumatrana* ranged from 25 to 48 μm and from 20 to 43 μm , respectively, and the average was $35 \pm 3 \mu\text{m}$ in fiber diameter and $31 \pm 3 \mu\text{m}$ in lumina diameter. In addition, the authors also mentioned that the fiber wall thickness of *S. sumatrana* ranged from 1 to 3 μm with an average of $2.3 \pm 0.4 \mu\text{m}$.

Table 3. Dimension and derivative value of tapped *S. sumatrana* wood fiber.

	Min	Max	Average	SD	Pulp Quality
Length (μm)	1113.25	1774.02	1390.77	180.27	(50) III
Diameter (μm)	24.04	34.72	29.23	3.07	-
Lumina diameter (μm)	14.69	24.37	17.99	3.08	-
Wall thickness (μm)	4.675	7.51	5.62	0.78	-
Runkel ratio	0.42	1.00	0.64	0.15	(50) III
Felting power	34.73	57.40	46.38	7.52	(50) III
Mulhsteph ratio (%)	50.73	74.98	62.13	6.53	(50) III
Coefficient of rigidity	0.15	0.25	0.19	0.03	(50) III
Flexibility ratio	0.50	0.70	0.61	0.05	(75) II
Total score					(320) II

RR is the double-cell-wall thickness ratio to the lumen diameter. A lower RR value is more favorable for producing high-quality fiber pulp, which is essential for achieving complete flatness and adequate fiber bonding in pulp sheets [25]. In the present study, the average RR of *S. sumatrana* wood was 0.64, and the RR ranged from 0.42 to 1.00, indicating a third-grade pulp quality. The RR in the present study demonstrated a lower pulp grade than that of *Styrax* wood reported in previous studies. Pasaribu et al. [18] reported a 0.15 RR in *S. sumatrana* and *S. paralleloneurus*, demonstrating the potential production of first-grade pulp. Damayanti et al. [21] reported that the RR of both tapped *S. benzoin* and untapped *S. paralleloneurus* was 0.14, which was another indicator of first-grade pulp.

The FP refers to the ratio of fiber length to diameter. A higher FP indicates a greater inter-fiber bonding and tear strength, which positively correlates with the tensile strength of paper sheets [25]. The FP of *S. sumatrana* wood was 46.38 and ranged from 34.73 to 57.40, showing third-grade pulp quality. The FPs of *S. sumatrana* and *S. paralleloneurus* were 52.42 and 47.70, respectively, in a previous study, indicating third-grade pulp quality [16]. The FP of tapped *S. benzoin* and untapped *S. paralleloneurus* revealed third-grade pulp quality at 52.09 and 53.12, respectively, in another study [21].

The MR refers to the ratio of the surface area of the fiber wall to the total surface area of the fiber. A smaller MR value leads to greater density in pulp sheets with high mechanical strength [25]. The MR of tapped *S. sumatrana* wood ranged from 50.73% to 74.98% and averaged 62.13% in this study, showing third-grade pulp quality. This MR demonstrated a lower pulp quality grade than that of *Styrax* wood reported in previous studies. Pasaribu et al. [18] reported an *S. sumatrana* and *S. paralleloneurus* MR of 24.35 and 23.72, respectively, demonstrating first-grade pulp quality. Similarly, the MR of tapped *S. benzoin* and untapped *S. paralleloneurus* showed first-grade pulp quality at 23.26 and 22.94, respectively [21].

The coefficient of rigidity (CR) is the ratio of the cell wall thickness to the fiber diameter, and a higher CR of a fiber reduces tensile strength [25]. The CR of tapped *S. sumatrana* ranged from 0.15 to 0.25, with an average value of 0.19 in the present study, showing third-grade pulp quality. However, this quality class was considerably lower than that of other *Styrax* woods reported in previous studies. The CR of untapped *S. sumatrana*, tapped *S. benzoin*, and untapped *S. paralleloneurus* was approximately 0.06, showing first-grade pulp quality [16,21].

The FR is the ratio of the lumen to fiber diameter. Here, the FR of tapped *S. sumatrana* ranged from 0.50 to 0.70, with an average of 0.61. However, it was lower than that of other *Styrax* wood reported in previous studies. The FR of untapped *S. sumatrana*, tapped

S. benzoin, and untapped *S. paralleloneurus* was approximately 0.88, showing first-grade pulp quality [16,21].

The total score of tapped *S. sumatrana* wood fibers in the present study demonstrated a second-grade pulp quality. In contrast, the total scores of untapped *S. sumatrana*, tapped *S. benzoin*, and untapped *S. paralleloneurus* showed first-grade pulp quality in previous studies [16,21].

4. Conclusions

The qualitative anatomical characteristics of tapped wood in the present study showed general characteristics of *Styrax* woods. TC formation was observed along the growth rings in the tapped part of the wood disc. The TC showed an irregular outline with 8–16 epithelial cells at the edges of the canal. Tapped *S. sumatrana* generally exhibited thin-walled fibers, whereas thick-walled fibers were observed near the TC. Furthermore, deposits were observed in some vessels in the tapped part but not in the untapped part.

Chambered prismatic oxalate crystals were observed in both axial and ray parenchyma, whereas silica grains were observed in ray cells. The fiber length and cell wall of tapped *S. sumatrana* were classified as moderate to extensive and thin to moderate, respectively. Moreover, the derivative value of the tapped *S. sumatrana* wood fibers indicated second-grade pulp quality.

In conclusion, the formation of TCs aligned tangentially was the most distinct characteristic of tapped *S. sumatrana* wood. The fiber quality of the tapped wood was categorized as second grade, which is acceptable for industry applications.

Author Contributions: Conceptualization, A.D., A.H.I., R.H. and A.S.; methodology, A.D. and B.D.P.; software, A.D. and B.D.P.; validation, A.H.I. and N.-H.K.; formal analysis, A.D. and B.D.P.; investigation, A.D. and B.D.P.; resources, A.H.I. and N.-H.K.; data curation, A.D. and B.D.P.; writing—original draft preparation, A.D. and B.D.P.; writing—review and editing, A.D., B.D.P., A.H.I. and N.-H.K.; visualization, A.D. and B.D.P.; supervision, A.H.I. and N.-H.K.; project administration, A.H.I. and N.-H.K.; funding acquisition, A.H.I. and N.-H.K. All authors have read and agreed to the published version of the manuscript.

Funding: This research was funded by the Deputy for Strengthening Research and Development, Ministry of Research and Technology/National Research and Innovation Agency, Republic of Indonesia, through the Basic Research of Higher Education Excellence (PDUP) Grant (Grant no. 11/AMD/E1/KP.PTNBH/2020, date: 11 May 2020). This study was also supported by the Science and Technology Support Program through the National Research Foundation of Korea (NRF) funded by the Ministry of Science and ICT (MSIT) (Grant no. 2022R1A2C1006470), the Basic Science Research Program through the NRF funded by the Ministry of Education (Grant no. 2018R1A6A1A03025582), and the R&D Program for Forest Science Technology (Project No. 2021350C10-2323-AC03) provided by the Korea Forest Service (Korea Forestry Promotion Institute).

Data Availability Statement: The datasets generated and analyzed in the current study are not publicly available but are available from the corresponding author upon reasonable request.

Conflicts of Interest: The authors declare no conflicts of interest.

References

1. Nussinovitch, A. *Plant Gum Exudates of the World: Sources, Distribution, Properties, and Applications*; CRC Press: Boca Raton, FL, USA, 2010.
2. Hoesen, D.S.H. Introduction. In *Plant Resources of South-East Asia*; Boer, E., Ella, A.B., Eds.; Plants Producing Exudates; Prosea: Bogor, Indonesia, 2001; Volume 18, pp. 13–44.
3. Langenheim, J.H. Plant resins. *Am. Sci.* **1990**, *78*, 16–24.
4. Langenheim, J.H. *Plant Resins: Chemistry, Evolution, Ecology, and Ethnobotany*; Timber Press: Portland, OR, USA, 2003.
5. Fritsch, P.W.; Morton, C.M.; Chen, T.; Meldrum, C. Phylogeny and biogeography of the Styracaceae. *Int. J. Plant Sci.* **2001**, *162*, S95–S116. [[CrossRef](#)]
6. Hoesen, D.S.H. *Styrax* L. In *Plant Resources of South-East Asia*; Boer, E., Ella, A.B., Eds.; Plants Producing Exudates; Prosea: Bogor, Indonesia, 2001; Volume 18, pp. 112–119.

7. Simamora, S.W.; Muhdi; Batubara, R. Modifikasi Teknik Pemanenan Dengan Perlakuan Fisik Dalam Upaya Peningkatan Produktivitas Getah Kemenyan Toba (*Styrax sumatrana*). *Peronema For. Sci. J.* **2015**, *4*, 159–165.
8. He, Q.; Sun, Y.; Chen, X.; Feng, J.; Liu, Y. Benzoin Resin: An Overview on Its Production Process, Phytochemistry, Traditional Use and Quality Control. *Plants* **2023**, *12*, 1976. [[CrossRef](#)] [[PubMed](#)]
9. Iswanto, A.H.; Susilowati, A.; Azhar, I.; Riswan, R.; Supriyanto, S.; Tarigan, J.E.; Fatriasari, W. Physical and mechanical properties of local *Styrax* woods from North Tapanuli in Indonesia. *J. Korean Wood Sci. Technol.* **2016**, *44*, 539–550. [[CrossRef](#)]
10. Badan Pusat Statistik Propinsi Sumatera Utara. *Indikator Pertanian Propinsi Sumatera Utara 2023*; Badan Pusat Statistik Propinsi Sumatera Utara: Medan, Indonesia, 2023.
11. Jayusman. *Recognising Incense Trees (Styrax spp.): Species with Broad Utilization Spectrums for Optimalization*; IPB Press: Bogor, Indonesia, 2014.
12. Dünisch, O.; Bass, P. On the origin of intercellular canals in the secondary xylem of selected *Meliaceae* species. *IAWA J.* **2006**, *27*, 281–297. [[CrossRef](#)]
13. Kuroda, K.; Shimaji, K. Traumatic resin canal formation as a marker of xylem growth. *Forest Sci.* **1983**, *29*, 653–659.
14. DeRose, R.J.; Bekker, M.F.; Long, J.N. Traumatic resin ducts as indicators of bark beetle outbreaks. *Can. J. For. Res.* **2017**, *47*, 1168–1174. [[CrossRef](#)]
15. Deng, X.Q.; Cheng, S.P.; Pan, N.X.; Chen, J.L. The effects of ethrel upon benzoin production and balsamic ducts of *Styrax hypoglauca* Perk. *J. Integr. Plant Biol.* **1978**, *20*, 26–29.
16. Pasaribu, G.; Jasni, J.; Damayanti, R.; Wibowo, S. Anatomical, physical, mechanical properties of Kemenyan Toba (*Styrax sumatrana*) and Kemenyan Bulu (*Styrax paralleloneurus*). *J. For. Prod. Res.* **2013**, *31*, 161–169.
17. Savero, A.M.; Kim, J.-H.; Purusatama, B.D.; Prasetya, D.; Park, S.-H.; Kim, N.-H. A Comparative Study on the Anatomical Characteristics of *Acacia mangium* and *Acacia hybrid* Grown in Vietnam. *Forests* **2022**, *13*, 1700. [[CrossRef](#)]
18. Franklin, G.L. Preparation of thin sections of synthetic resins and wood resin composites, and a new macerating method for wood. *Nature* **1945**, *155*, 51–59. [[CrossRef](#)]
19. Nurachman, R.; Siagian, M. *Dimensi Serat Jenis Kayu Indonesia*; Laporan No. 75; Lembaga Penelitian: Bogor, Indonesia, 1976.
20. Adi, D.S.; Wahyuni, I.; Risanto, L.; Ruliaty, S.; Hermiati, E.; Dwianto, W.; Watanabe, T. Central kalimantan's fast growing species: Suitability for pulp and paper. *Indonesian J. For. Res.* **2015**, *2*, 21–29. [[CrossRef](#)]
21. Damayanti, R.; Mandang, Y.I.; Waluyo, T.K. Anatomical properties and fiber quality of *Styrax* stem from North Sumatra. *J. For. Prod. Res.* **2007**, *25*, 273–290.
22. Dickison, W.C.; Phend, K.D. Wood anatomy of the *Styracaceae*: Evolutionary and ecological considerations. *IAWA J.* **1985**, *6*, 3–22. [[CrossRef](#)]
23. IAWA Committee. *IAWA List of Microscopic Features for Hardwood Identification with an Appendix on Non-Anatomical Information*; National Herbarium of the Netherlands: Leiden, The Netherlands, 1989; pp. 219–332.
24. Machado, S.R.; Rodella, R.A.; Angyalossy, V.; Marcatti, C.R. Structural variations in root and stem wood of *Styrax* (*Styracaceae*) from Brazilian forest and cerrado. *IAWA J.* **2007**, *28*, 173–188. [[CrossRef](#)]
25. Darwis, A.; Karliati, T.; Sutrisno Alamsyah, E.M.; Rumidatul, A.; Melani, L.; Kim, H.J.; Iswanto, A.H.; Fatriasari, W. Chemical properties, crystallinity, and fiber biometry of Jabon (*Anthocephalus cadamba*) wood for pulp raw material: The effect of age and position. *Nord. Pulp Pap. Res. J.* **2024**, *39*, 67–71. [[CrossRef](#)]

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.